

Препринти Інституту фізики конденсованих систем НАН України розповсюджуються серед наукових та інформаційних установ. Вони також доступні по електронній комп'ютерній мережі на WWW-сервері інституту за адресою <http://www.icmp.lviv.ua/>

The preprints of the Institute for Condensed Matter Physics of the National Academy of Sciences of Ukraine are distributed to scientific and informational institutions. They also are available by computer network from Institute's WWW server (<http://www.icmp.lviv.ua/>)

Тарас Миколайович Пацаган
Мирослав Федорович Головка

МОЛЕКУЛЯРНА ДИНАМІКА ВОДНОГО РОЗЧИНУ УРАНІЛУ В
ГІДРОФІЛЬНІЙ НАНОПОРІ: ВИПАДОК ЩІЛИНОПОДІБНОЇ ПОРИ
АМОРФНОГО КРЕМНЕЗЕМУ

Роботу отримано 23 листопада 2006 р.


Затверджено до друку Вченою радою ІФКС НАН України

Рекомендовано до друку семінаром відділу теорії розчинів

Виготовлено при ІФКС НАН України

© Усі права застережені

Національна академія наук України

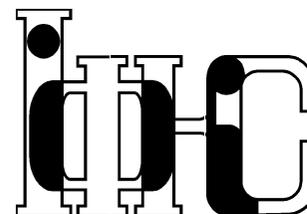

ІНСТИТУТ
ФІЗИКИ
КОНДЕНСОВАНИХ
СИСТЕМ

ICMP-06-23E

T. Patsahan, M. Holovko

Molecular dynamics study of aqueous uranyl in hydrophilic
mesoporous confinement: The case of slit-like pore in amorphous
silica

ЛЬВІВ

УДК: 532.546; 532.72

PACS: 02.70.Ns, 68.43.Jk, 82.70.Gg

Molecular dynamics study of aqueous uranyl in hydrophilic mesoporous confinement: The case of slit-like pore in amorphous silica

T. Patsahan, M. Holovko

Abstract. Molecular dynamics simulations are used to study structural and dynamic properties of water and aqueous uranyl ion adsorbed in a slit-like pore of amorphous silica. Calculations are performed for the flexible SPC/E water model in the atomistically detailed pores with sizes in the range of 2.0-5.0 nm. The hydroxyl groups on the pore surfaces lead to the strong adsorption and affect strongly a mobility of water molecules. The uranyl ion and its aqueous environment adsorbed in the pores are studied at the room temperature, for different amount of water. The effect of hydroxylated silica pores on the formation of uranyl hydrate complexes is discussed within this study.

Молекулярна динаміка водного розчину уранілу в гідрофільній нанопорі: Випадок щілиноподібної пори аморфного кремнезему

Т. Пацаган, М. Головко

Анотація. Використовуючи метод молекулярної динаміки досліджено структурні та динамічні властивості води і водного розчину іона уранілу адсорбованих в щілиноподібній порі аморфного кремнезему. Розрахунки проводилися для випадку гнучкої моделі води SPC/E в атомарно деталізованій порі, розміри якої вибирались в межах 2.0-5.0 нм. Наявність гідроксильних груп розташованих на поверхні пори, приводить до сильної адсорбції молекул води, що має визначальний вплив на їх динаміку. Детально вивчено випадок іона уранілу поблизу стінки пори і вплив гідроксильних груп на формування його гідратної оболонки.

Подається в Journal of Molecular Liquids
Submitted to Journal of Molecular Liquids

© Інститут фізики конденсованих систем 2006
Institute for Condensed Matter Physics 2006

1. Introduction

Besides the fundamental interest, a study of radionuclides adsorbed in pores of various materials based on SiO₂ is of great practical importance, especially from the ecological point of view. The most applied problems considered are aimed to prevent large area pollution caused by radioactive compounds that can migrate through minerals composing soils and subsurface sediments from the sites where the radionuclides are concentrated: uranium deposits and uranium ore milling sites, nuclear wastes repositories and sites of nuclear accidents. Uranium is a major contaminant since it is a predominant heavy metal content of spent nuclear fuel. Dissolved uranium dioxide is mostly hexavalent and it can be very mobile in the water environment depending on the material in which it is confined. The dioxide of hexavalent uranium is known as uranyl (UO₂²⁺) and it is positively charged, thus a coulombic interaction is very important in such systems. We present a study of some dynamic and structural properties of uranyl ion and its water environment that are affected by a pore of silica in which they are adsorbed. While one can find numerous experimental results for uranyl ion in various environments, there are not so much investigations where the uranyl ion interacting with some substrate is considered using the methods of computer simulations. A molecular dynamics study of aqueous uranyl near α -quartz surface was presented by Greathouse et al. [1], where a number of radial distribution functions were obtained for different configurations of uranyl and its hydrate and carbonato complexes. The self-diffusion coefficients of water molecules in different layers relatively to the quartz surface were calculated. Later, the computer simulations were performed [2, 3] in order to study a sorption of the aqueous uranyl on the clay mineral of montmorillonite. In contrast to the previous studies where substrate surface had an ordered structure, we focus on amorphous one since we are interested in the problems concerned with uranyl ion transport and the properties of its aqueous environment in the so-called lava-like fuel-containing materials formed in the reactor building of Chornobyl Nuclear Power Plant in the consequence of well known heavy nuclear accident which occurred in 1986. The lava-like fuel-containing materials have a complicated structure and contain various compounds, but in general they consist of high-radioactive silica glasses. The pores in these glasses form a disordered network of meso-scaled channels, where different kinds of dissolved radionuclides and other light and heavy metals can migrate through. Recently, we presented a study of water dynamics in the model disordered porous material [4], but in the current study we concentrate

on the partial case of a confinement, namely on the single-pore model. In this case we neglect a randomness of porous medium for better comprehension of structural and dynamic properties of water and aqueous uranyl in one separate pore. In this way we can try to understand better different mechanisms of the influence of porous silica on uranyl ion and its aqueous environment. A slit-like pore model of amorphous silica with atomistically detailed structure is chosen. The surfaces of pore are saturated by hydroxy groups which appear in the result of the chemical reactions of water with non-bonded oxygens on the silica surface. Therefore, the pore is hydrophilic and adsorption effects are anticipated. We also consider the cases when hydroxyls are partially or completely removed from the surfaces. The several widths of meso-pore are studied to demonstrate an size effect of confinement on the water density profiles and to see how this affects uranyl sorption dynamic. The average values of self-diffusion coefficients are calculated in the hydrophobic and hydrophilic pore of size 2 nm.

2. Model and simulation details

The pore is modelled as a space between two slabs of amorphous silica. The space between these slabs is filled by water molecules of some density. An uranyl ion is involved in the equilibrated aqueous environment. During a simulation processes the values of (x, y, z)-coordinates of uranyl ion are stored to analyze its trajectories, while the averaged radial distribution functions, water density profiles and mean-square displacement functions were produced during simulation runs. The whole system is atomistically detailed, therefore all the pair interactions in the system can be described in a realistic way, although in this case the simulations are quite time consuming and cannot be very long-time scaled.

The model of amorphous silica is prepared using molecular dynamics simulation. The β -cristobalite of SiO_2 is chosen as the base atomic structure of silica slab which consists of 5400 atoms and the slab size is about $50 \times 43 \times 32 \text{ \AA}$. The pair interaction between atoms is described by the Morse potential with the parameters given in ref. [5]. All simulations are performed in the constant (NVT) ensemble with periodic boundary conditions. Amorphous silica is obtained from crystalline one following the regime 1-XIII in ref. [5], which includes a heating crystalline structure of SiO_2 to the temperature 8000 K and a sequential cooling to the room temperature. After equilibration of the system at 300 K during 40 ps, the resulted sample is kept at the temperature 300 K and the constant pressure 1 atm. The total time of the heating/cooling processes takes

310 ps. At the final stage, to make a silica surface relax the simulation run of the prepared structure is performed during 50 ps without periodic boundary conditions in z-direction.

The next step concerns a preparation of silica surface. We remove from the silica surface all silicon atoms that are bonded the less than four oxygens like it was proposed in refs. [6,7]. To saturate free bonds of non-bridging oxygen atoms (O_h), hydrogens are attached to each O_h at the distance of 1.0 \AA and the average Si-O-H angle 116° . In our study the obtained number density of hydroxy groups on the surface is around 4.9 OH/nm². This value is in a good agreement with theoretical and experimental data for amorphous silica [8–10]. After that, a silica slab is cut off from the obtained sample. Thereby, two identical silica slabs with thickness of $\sim 15 \text{ \AA}$ are used to construct two parallel walls of slit-like pore with a width of $d=2 \text{ nm}$ and boundary conditions in x and y directions. The prepared pore can be filled of water molecules of corresponding densities. The different densities of water in the pores are considered. The uranyl ion UO_2^{2+} is involved in the pore as well. To describe an interaction between atoms in the system the pair potentials and the partial charges are used accordingly to ref. [1], where the interaction parameters between uranyl ion and water molecules were chosen following Guilbaud and Wipff [11]. However, in order to provide an electroneutrality in the whole system the original values of silicon and oxygen atom charges were slightly adjusted. During the simulation of water and aqueous uranyl ion in the pore, the silica structure stay stationary, e.g. the coordinates of silicon and oxygen atoms are fixed, except hydrogen atoms in hydroxyl groups –OH connected with corresponding non-bridging oxygen atoms by flexible bonds. In contrast to [1], where as a water model the flexible version of SPC model was used, we prefer flexible SPC/E one [12]. We noticed, that flexible SPC model gives highly overestimated values for a self-diffusion coefficient of water molecules, while the self-diffusion coefficient of SPC/E water in bulk is much closer to the known experimental data ($2.3 \cdot 10^{-9} \text{ m}^2/\text{s}$), although a little bit lower ($2.0 \cdot 10^{-9} \text{ m}^2/\text{s}$). The bonds between uranium and oxygen atoms in UO_2^{2+} are considered flexible as well [1]. The snapshot of simulation box with the model system of aqueous uranyl in the hydrophilic silica pore is presented in Fig. 1. The potentials and the corresponding parameters for interatomic interactions are presented in Table 1 in ref. [1].

To study the density profile of water and its effect on transport phenomena in the pore the different pore loadings of water molecules are considered. The water density varies in the range 0.21-1.00 g/cm³. The computer simulations of water and aqueous uranyl in the slit-like pore of

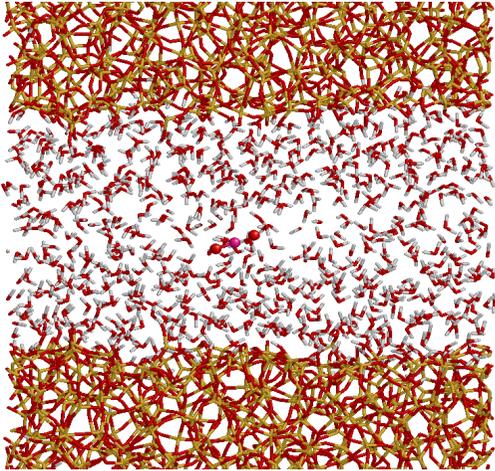


Figure 1. A snapshot of the simulated system. The uranyl ion (in the center) and water in the slit-like pore of amorphous silica.

silica are performed using the method of molecular dynamics at the constant temperature $T=300$ K in (N,V,T) ensemble with two-dimensional boundary conditions. The interaction cutoff distance 10 Å with long range correction is used. Also the two-dimensional version of Ewald summation algorithm for electrostatic interactions is applied. The average values of the desired temperatures were maintained using the algorithm according to the Nosé-Hoover thermostat with a relaxation time constant $t^* \sim 0.1$ ps while the simulation time step, Δt , was set to 0.0005 ps. The time of the system equilibration was 100 ps. During the production time, 600 ps, the averaged radial distribution functions and the mean-square displacement functions are calculated. The functions obtained allow us to analyze the structural and dynamic properties of components of the system. A random removal of certain number of hydroxyl groups from the silica surface changes hydrophilicity of the pore walls. A complete dehydroxylation leads to the hydrophobicity of the pore due to the absence of polar groups on the surface.

3. Results and discussion

Considering water of various densities in the hydrophilic pore, the adsorption effect on the pore surfaces is distinguished. This effect can be

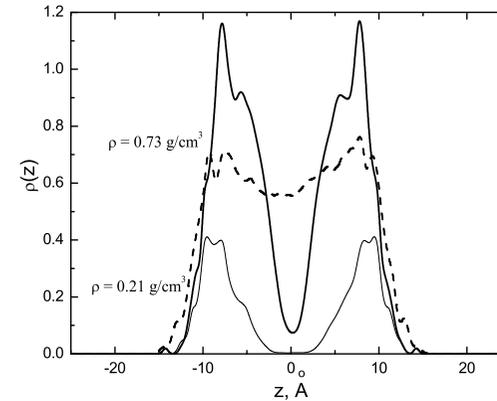


Figure 2. The water density profiles for the different pore loadings. The dashed line corresponds to the case of the hydrophobic pore and for water density $\rho_w=0.73$ g/cm³.

illustrated by the water density profiles in Fig. 2. The sharp peaks of the water density profiles indicate that the layering of the water molecules appears near the pore walls for the water densities 0.21 g/cm³ and 0.73 g/cm³. Due to hydrophilic nature of surface all water molecules are attracted towards of pore surface. In all cases one can observe a lower density at the center of pore ($z \sim 0.0$) than for bulk water. In the case of a small amount of water (for example, $\rho=0.21$ g/cm³) the water molecules can be practically absent in the pore center.

In Figs. 3 and 4 one can see the water density profiles depending on the pore size. If the pore size is quite large (more than 5 nm), the water molecules in the center of the pore are not affected by the pore walls and the density profile is uniform in the case of completely loaded pore. Therefore, a behavior of the water molecules in this region can be treated in the same way as in the bulk. When the pore size decreases, the water density is very inhomogeneous and it becomes very important on which distance to the wall the water molecules and the uranyl ion are considered. In this study, two locations of uranyl ion are studied – in the center of the pore and near the pore surface. When uranyl ion is far from the pore surface, it is not affected directly by hydroxyl groups. But when it is near the surface, the binding of uranyl ion and corresponding hydroxyl can occur. This binding is accompanied by changes in the hydration shell of the ion. The hydroxyl group is involved into the hy-

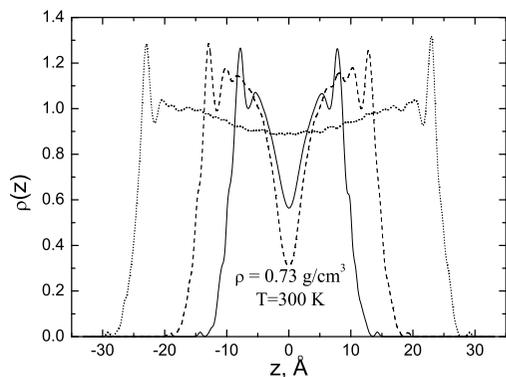


Figure 3. The water density profiles for the different pore sizes (2–5 nm).

dration shell during the binding process, while one of the five molecules of hydration shell leaves the ion. The radial distribution functions that illustrate the mentioned effects are presented in Fig. 5.

The density profile of water molecules has a significant effect on the dynamics of the uranyl ion in the pore. It is noticed that the uranyl ion, placed initially in the pore center, keeps the central area of the pore during the simulation run and moves together with its hydrate complex in the XY surface, e.g. along the pore. The hydrate complex has a pentagonal symmetry, the same symmetry as in the case of uranyl ion in bulk water (Fig. 5a). The hydrate shell of the uranyl ion consists of five molecules of water. It was noticed, the binding between the uranyl ion and the pore wall can appear when the ion is initially placed at the distance of $\sim 2\text{\AA}$ to the wall. In this case the hydroxyl of silica surface replaces one of the five molecules of water in the hydrate shell of the uranyl. This phenomenon is illustrated by the corresponding averaged radial distribution functions and the running coordination numbers in Fig. 5b. Despite the attraction between uranyl ion and the pore walls the uranyl ion does not bind with the pore surface by itself when it is far enough ($\gtrsim 4\text{\AA}$). This can be explained by the adsorption phenomena that lead to the formation of the dense layer of water, which resists the penetration of the uranyl ion towards the wall. In the case of the hydrophobic pore, when the water density is distributed more or less uniformly in the pore volume (Fig. 2, dashed line), the uranyl ion migrates easily to the pore surface and the close vicinity of the uranyl ion to the pore surface reduces its mobility. In all cases a pentagonal hydrate

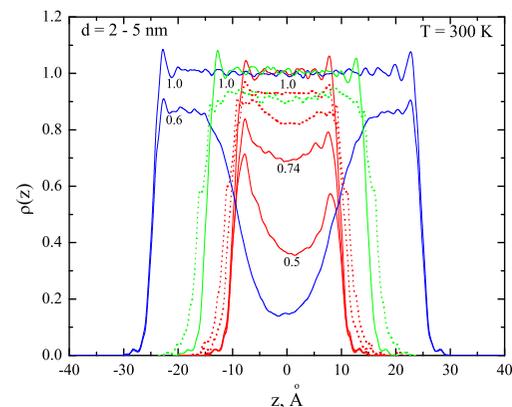


Figure 4. The water density profiles for the different pore sizes (2–5 nm) and the different surface density of hydroxyl groups. Dotted lines correspond to the partly hydrated surface of the pores.

shell formed at the distance of $\sim 2.51\text{--}2.52\text{\AA}$ to the center of uranyl ion is observed. Such a configuration is already observed in the previous studies by molecular dynamics simulation [1] as well as by quantum chemistry calculations [13].

When the water density in the pore increases to 1 g/cm^3 , the uranyl ion initially placed in the pore center reaches rapidly the pore surface area (Fig. 6) like it was observed in the hydrophobic case before. It can be explained by the density profile uniformity along z-direction (Fig. 4). However, similar to the previous case, the uranyl ion, being near the pore surface, cannot bind with hydroxyl group by itself due to its hydration shell that needs some charge redistribution, which should appear in such complexes. The method of classical molecular dynamics cannot provide any charge redistribution, because this is a kind of quantum mechanics problem, thus some extensions should be applied to take this effect into account. In our study all charges are fixed, therefore the whole adsorption process could not be observed in dynamics. But, when the uranyl ion is placed at the distance $\sim 2\text{--}3\text{\AA}$ to the silica surface, it binds easily with a corresponding hydroxyl group and keeps on its place for a long time during simulation runs ($\gg 1000\text{ ps}$).

In Fig. 6 one can see a number of z-trajectories of uranyl ion, which is adsorbed in the pores of the different sizes (2–5 nm). It is shown that in the narrow pore (2 nm), the uranyl ion moves fast towards the pore

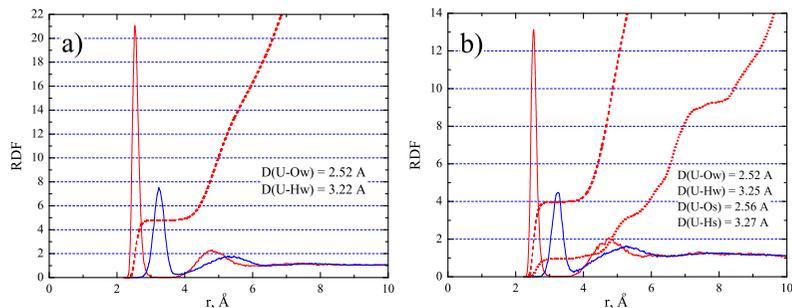


Figure 5. The radial distribution functions U-Ow for the aqueous uranyl and its hydration shell in a slit like pore of amorphous silica at the temperature 300 K: (a) uranyl ion in the center of the pore; (b) uranyl ion near the surface of pore wall.

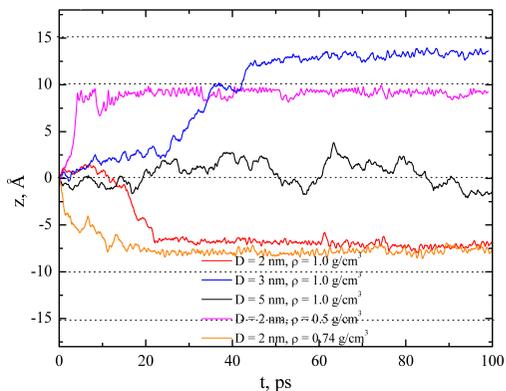


Figure 6. z-trajectories of uranyl ion in the pores of different sizes and loadings.

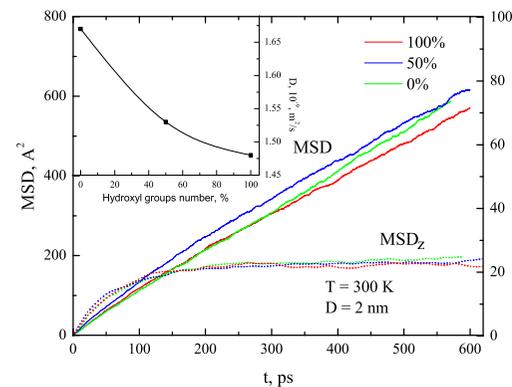


Figure 7. The mean-square displacement functions and the total self-diffusion coefficients of water molecules in the slit like pore of amorphous silica for the different levels of the pore hydrophilicity. The pore size is equal to 2 nm.

wall. When the pore increases the averaged velocity of uranyl ion in z-direction decreases. Moreover, a time delay appears before the ion begins to move to the wall. When the pore size is of 5 nm, the uranyl ion located in the middle of the pore becomes indifferent to the pore walls. Moving around, the uranyl ion can approach to one of the walls, but the time needed to do that is much larger – more than a few orders of magnitude than in the case of 2 nm and 3 nm. A tendency to the motion of the ion towards the wall was not observed even after 1000 ps.

As a result, the effect of the pore hydrophilicity on the water dynamics, the averaged values of the total self-diffusion coefficient of the water molecules in the pore of 2 nm and the different surface densities of hydroxyl groups should be obtained. For this purpose the functions of mean-square displacement (MSD) are calculated (Fig. 7). The three values of the surface densities of hydroxyls are chosen, that correspond to the full hydroxylated surface (100% or 4.9 OH/nm² for the system considered), partial hydroxylated (2.5 OH/nm²) and completely dehydroxylated surface (0%). The self-diffusion increase is observed when the surface density of hydroxyls decreases. The dashed lines denote MSD functions in z-direction. This particular form of the MSD functions is appropriate to the case of the molecular dynamics in confined space, where the motion in some directions is restricted by the pore walls and the maximum value of the MSD function, which is reached in this case,

defined by a pore size. The calculated values of the self-diffusion coefficient are close to that predicted in refs. [14, 15] for water adsorbed in Vycor-like glass at the similar conditions.

4. Conclusions

The model of a slit like pore of silica is considered within this study. The water density profiles are obtained to study an effect of the pore size and its loadings on the uranyl ion dynamics. If the pore is narrow (2-3 nm) and the loading is close to 1 g/cm³ of the water density, the uranyl ion adsorbs on the pore surface very fast. In the hydrophobic pore the uranyl ion reaches the surface of a partly loaded pore faster than in the hydrophilic one. However, in the hydrophobic pore, where hydroxyl groups are absent, the ion cannot associate with the surface.

The significant effect of the arrangement of the water molecules in pore on the uranyl ion behavior and its hydration shell inspired us to consider them depending on the pore parameters. The layering structure of the density of water molecules near the pore surface are observed in the hydrophilic pore. The first peak in the water density profile becomes lower when the surface density of hydroxyls decreases. Moreover, the water density distribution through the pore volume is more homogeneous when we have a small amount of the hydroxyl groups on the surface. In the case of partially loaded pore the water molecules are practically absent in the center of the pore. When the pore surface is hydrophobic (small amount of hydroxyl groups), the difference between the densities of water molecules in center and near surface of the pore is much smaller. In the pore that partially loaded by water molecules one can see a high inhomogeneity of water density which is caused by adsorption of water molecules on the hydrophilic pore surface. Because of the small amount of water that cannot fill the whole pore, one can notice an asymmetry in the water density profile. An asymmetric profile indicates that the most part of water molecules prefers one of the two pore walls in the time interval observed. In the case of a pore completely loaded by water molecules ($\rho=1$ g/cm³) the average self-diffusion coefficient of water decreases when the surface density of hydroxyl groups increases.

The aqueous uranyl ions confined in the silica pore attract to the pore walls and binds with silica surface. Due to the strong association, the uranyl ion keeps on the silica surface for a long time. A reverse process (e.g. disconnection of uranyl ion) was not observed during simulation runs (>600 ps). Near the silica surface, the hydrate shell of uranyl ion consists of four water molecules and one hydroxyl group bearing on the

surface. A complex of four water molecules and one hydroxyl group was obtained only when uranyl ion was placed at the distance $\sim 2\text{\AA}$ from the silica surface.

The report presented here is mostly preliminary and should be extended and perhaps is to be studied more deeper in some directions. However, the obtained results gives us a flavor of the structure and dynamics peculiarities in the system considered. The problems appeared during this study suggest to make some modifications related to the model of the system as well as to the simulation process itself. The first methodical problem concerns the charge redistributions during the binding processes of uranyl ion and water/hydroxyl that should be taken into account to describe adsorption process correctly. Another problem consists in the large time consumption to simulate a dynamics in such systems. Being a very heavy compound comparing with water molecules, the uranyl ion has an extremely slow dynamics that cannot be observed properly during relatively short-time scale simulations (~ 1000 ps) within the framework of the model considered in this study. Therefore, a more simple model of silica structure is needed, where the number of sites of interaction are much less.

5. Acknowledgements

TP thanks the World Federation of Scientists and ICSC "World Laboratory" for the partial financial support within the framework of the National Scholarship Program. The computational facilities were provided by the computing cluster of the Institute for Condensed Matter Physics.

References

1. J.A. Greathouse, R.J. O'Brien, G. Bemis, R.T. Pabalan, *J. Phys. Chem. B*, 106 (2002) 1646.
2. O.F. Zaidan, J.A. Greathouse, R.T. Pabalan, *Clays and Clay Minerals*. 51 (2003) 372.
3. J.A. Greathouse, R.T. Cygan, *Phys. Chem. Chem. Phys.* 7 (2005) 3580.
4. T. Patsahan, M. Holovko, *Condens. Matter Phys.* 7 (2004) 3.
5. N.T. Huff, E. Demiralp, T. Cagin, W.A. Goddard, *J. Non-Cryst. Solids*. 253 (1999) 133.
6. A. Brodka, T.W. Zerda, *J. Chem. Phys.* 105 (1996) 6319.

7. M. Rovere, M.A. Ricci, D. Vellati, F. Bruni, *J. Chem. Phys.* 108 (1998) 9859.
8. S.H. Lee, P.J. Rossky, *J. Chem. Phys.* 100 (1994) 3334.
9. N.D. Zhuravlev, J.I. Siepmann, M.R. Schure, *Anal. Chem.* 21 (2001) 4006.
10. R.K. Iler, *The Chemistry of Silica*, Wiley, New York, 1979.
11. P. Guilhaud, G. Wipff, *J. Mol. Struct.* 366 (1996) 55.
12. H.J.C. Berendsen, J.P.M. Postma, W.F. van Gunsteren, A. Di Nola, J.R. Haak, *J. Chem. Phys.* 81 (1984) 3684.
13. I.M. Krip, T.V. Shymchuk, I.V. Stasyuk, T.S. Mysakovich, Preprint ICMP, ICMP-04-14E (2004).
14. P. Gallo, *Phys. Chem. Chem. Phys.* 2 (2000) 1607.
15. M.-C. Bellissent-Funel, *Eur. Phys. J.* 12 (2003) 83.

CONDENSED MATTER PHYSICS

The journal **Condensed Matter Physics** is founded in 1993 and published by Institute for Condensed Matter Physics of the National Academy of Sciences of Ukraine.

AIMS AND SCOPE: The journal **Condensed Matter Physics** contains research and review articles in the field of statistical mechanics and condensed matter theory. The main attention is paid to physics of solid, liquid and amorphous systems, phase equilibria and phase transitions, thermal, structural, electric, magnetic and optical properties of condensed matter. *Condensed Matter Physics* is published quarterly.

ABSTRACTED/INDEXED IN:

- Chemical Abstract Service, Current Contents/Physical, Chemical&Earth Sciences
- ISI Science Citation Index-Expanded, ISI Alerting Services
- INSPEC
- Elsevier Bibliographic Databases (EMBASE, EMNursing, Compendex, GEOBASE, Scopus)
- "Referativnyi Zhurnal"
- "Dzherelo"

EDITOR IN CHIEF: Ihor Yukhnovskii

EDITORIAL BOARD: T. Arimitsu, *Tsukuba*; J.-P. Badiali, *Paris*; B. Berche, *Nancy*; J.-M. Caillol, *Orsay*; C. von Ferber, *Freiburg*; R. Folk, *Linz*; D. Henderson, *Provo*; Yu. Holovatch, *Lviv*; M. Holovko, *Lviv*; O. Ivankiv, *Lviv*; M. Korynevskii, *Lviv*; Yu. Kozitsky, *Lublin*; M. Kozlovskii, *Lviv*; H. Krienke, *Regensburg*; R. Levitskii, *Lviv*; V. Morozov, *Moscow*; I. Mryglod, *Lviv*; O. Patsahan (Assistant Editor), *Lviv*; N. Plakida, *Dubna*; G. Röpke, *Rostock*; Yu. Rudavskii, *Lviv*; I. Stasyuk (Associate Editor), *Lviv*; M. Tokarchuk, *Lviv*; I. Vakarchuk, *Lviv*; M. Vavruk, *Lviv*; A. Zagorodny, *Kyiv*.

CONTACT INFORMATION:

Institute for Condensed Matter Physics
of the National Academy of Sciences of Ukraine
1 Svientsitskii Str., 79011 Lviv, Ukraine
Tel: +380(322)760908; Fax: +380(322)761158
E-mail: cmp@icmp.lviv.ua <http://www.icmp.lviv.ua>